



# FREIOTHERM-KTL-Special

## WK4128HB3001

<b>Characteristics</b>	<ul style="list-style-type: none"> <li>■ Cathodic electrocoat paint depositable 2K</li> <li>■ Application, e.g. in the construction and sanitary sector</li> <li>■ Pigment paste, fully neutralised</li> <li>■ Primer</li> <li>■ Good corrosion protection</li> </ul>	
<b>Technical / Physical Data</b>	<ul style="list-style-type: none"> <li>■ Binder-Base</li> </ul>	Expoxy Resin, modified
	<ul style="list-style-type: none"> <li>■ Colour</li> </ul>	radiatoren white Based on the specified colour template (i.e. RAL)
	<ul style="list-style-type: none"> <li>■ Solid Mass DIN EN ISO 3251</li> </ul>	63-67 %
	<ul style="list-style-type: none"> <li>■ Density calculated</li> </ul>	1,62 g/cm <sup>3</sup>
	<ul style="list-style-type: none"> <li>■ MEQ/s-Value</li> </ul>	30-35 mmol/100g
	<ul style="list-style-type: none"> <li>■ Viscosity</li> </ul>	1300-3300 mPa.s
	<ul style="list-style-type: none"> <li>■ Test layer thickness</li> </ul>	8-12 µm
<b>Mechanical Test</b>	<ul style="list-style-type: none"> <li>■ on iron phosphating</li> </ul>	
	<ul style="list-style-type: none"> <li>■ Cross-cut-test DIN EN ISO 2409</li> </ul>	Gt 0
<b>Resistance Test</b>	<ul style="list-style-type: none"> <li>■ on iron phosphating</li> </ul>	
	<ul style="list-style-type: none"> <li>■ Condensate constant climate DIN EN ISO 6270-2 (CH)</li> </ul>	504 hours water ingress Wb <1 mm DIN EN ISO 4628-8
	<ul style="list-style-type: none"> <li>■ Salt spray test (NSS) DIN EN ISO 9227</li> </ul>	240 hours water ingress Wb <2 mm DIN EN ISO 4628-8
<b>Processing and application</b> Dependent on plant and buildings	<ul style="list-style-type: none"> <li>■ <b>Pretreatment</b> The substrate must be free of adhesion-impairing substances such as oil, grease, rust, scale, rolling skin, wax and separating agent residue. For more demanding requirements on corrosion inhibiting properties, we recommend suitable conversion processes (e.g. phosphatizing).</li> </ul>	
	<ul style="list-style-type: none"> <li>■ Mixing ratio</li> </ul>	The mixing ratio is dependent on various factors and is therefore coordinated with the relevant system in cooperation with the application technology department.
	<ul style="list-style-type: none"> <li>■ Gloss value DIN EN ISO 2813</li> </ul>	70-90 geometry 60°
	<ul style="list-style-type: none"> <li>■ pH-Value</li> </ul>	4,8-5,8
	<ul style="list-style-type: none"> <li>■ Cunductance</li> </ul>	1800-2200 µS/cm
	<ul style="list-style-type: none"> <li>■ Solid Mass DIN EN ISO 3251</li> </ul>	17-21 %
	<ul style="list-style-type: none"> <li>■ MEQ/b-Value</li> </ul>	6,5-7,5 mmol/100 g
	<ul style="list-style-type: none"> <li>■ Organic Solvent Content</li> </ul>	1,3-3,0 %



## FREIOTHERM-KTL-Special WK4128HB3001

- Bath Temperature 28-32 °C
- Coating Time 60-180 seconds
- Deposition Voltage 170-300 voltage

### ■ Health & Safety at Work guidelines

The standard personal safety precautions must be observed when handling painting materials. Detailed information about dangerous goods, safety data and recommendations concerning Health & Safety at Work and environmental protection can be found in the corresponding safety data sheet.


### Curing

### ■ Object temperature

Recommended baking temperature 20 Min./170 °C

green cross-hatching = baking conditions with good final properties

Objekt Temperatur   °C Object Temperature   °C	160	170	180
Haltezeit Minimum   Minuten Holding time minimum   Minutes	30	20	10
Haltezeit Maximum   Minuten Holding time maximum   Minutes	40	30	20

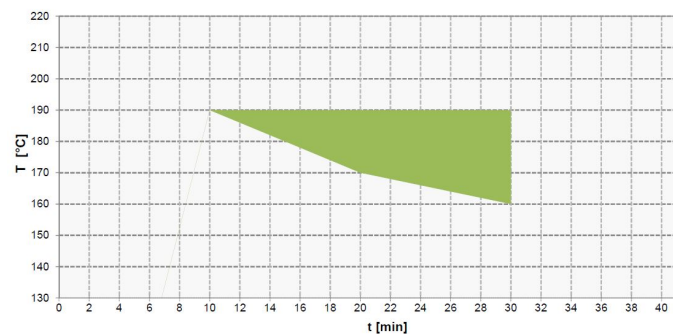

### Resistance to storage

### ■ One Turn-Over per year

Approx. 9 month in original packagings at an ambient temperature of 5 to 25 °C. Protect from frost. Open packages are to be used within a short time.

The minimum storage stability of each batch is stated on the product label. The material does not necessarily become unusable if stored for longer than this period. However, for quality assurance purposes, an inspection of these materials is essential to ensure that they are still suitable for the intended application.

### Specific comments

### ■ Test conditions

All information is based on a standard climate 23/50 DIN EN 23270.

All information is based on our product knowledge and experience. We have no direct influence on the application itself. Please do not hesitate to contact us for further information.

The information provided here contains reference values and does not constitute a specification.